

# Visualization of the emergence of the pseudogap state and the evolution to superconductivity in a lightly hole-doped Mott insulator

Y. Kohsaka<sup>1\*</sup>, T. Hanaguri<sup>2</sup>, M. Azuma<sup>3</sup>, M. Takano<sup>4</sup>, J. C. Davis<sup>5,6,7,8</sup> and H. Takagi<sup>1,2,9</sup>

**Superconductivity emerges from the cuprate antiferromagnetic Mott state with hole doping. The resulting electronic structure<sup>1</sup> is not understood, although changes in the state of oxygen atoms seem paramount<sup>2–5</sup>. Hole doping first destroys the Mott state, yielding a weak insulator<sup>6,7</sup> where electrons localize only at low temperatures without a full energy gap. At higher doping levels, the ‘pseudogap’, a weakly conducting state with an anisotropic energy gap and intra-unit-cell breaking of 90° rotational ( $C_{4v}$ ) symmetry, appears<sup>3,4,8–10</sup>. However, a direct visualization of the emergence of these phenomena with increasing hole density has never been achieved. Here we report atomic-scale imaging of electronic structure evolution from the weak insulator through the emergence of the pseudogap to the superconducting state in  $Ca_{2-x}Na_xCuO_2Cl_2$ . The spectral signature of the pseudogap emerges at the lowest doping level from a weakly insulating but  $C_{4v}$ -symmetric matrix exhibiting a distinct spectral shape. At slightly higher hole density, nanoscale regions exhibiting pseudogap spectra and 180° rotational ( $C_{2v}$ ) symmetry form unidirectional clusters within the  $C_{4v}$ -symmetric matrix. Thus, hole doping proceeds by the appearance of nanoscale clusters of localized holes within which the broken-symmetry pseudogap state is stabilized. A fundamentally two-component electronic structure<sup>11</sup> then exists in  $Ca_{2-x}Na_xCuO_2Cl_2$  until the  $C_{2v}$ -symmetric clusters touch at higher doping levels, and the long-range superconductivity appears.**

To visualize at the atomic scale how the pseudogap and superconducting states are formed sequentially from the weak insulator state, we performed spectroscopic imaging scanning tunnelling microscopy (SI-STM) studies on  $Ca_{2-x}Na_xCuO_2Cl_2$  ( $0.06 \leq x \leq 0.12$ ; see also the Methods sections). The crystal structure is simple tetragonal ( $I4/mmm$ ) and thereby advantageous because the  $CuO_2$  planes are unbuckled and free from orthorhombic distortion. More importantly  $Ca_2CuO_2Cl_2$  can be doped from the Mott insulator to the superconductor by introduction of Na atoms. Figure 1c,d shows differential conductance images measured using SI-STM of bulk-insulating  $x = 0.06$  and  $x = 0.08$  samples taken in the field of views of the topographic images in Fig. 1a,b. The wavy, bright, arcs in Fig. 1c,d have never been observed in superconducting samples ( $x > 0.08$ ) but appear only in such quasi-insulating samples ( $x \leq 0.08$ ). They are created by

spectral peaks in differential conductance spectra whose energy is dependent on location (Fig. 1f). Consequently, the wavy arcs shrink with increasing bias voltages and finally disappear. This behaviour, due to tip-induced impurity charging<sup>12–14</sup>, is characteristic of poor electronic screening in a weakly insulating state.


A wide variety of spectral shapes originating from electric heterogeneity were found in these samples. A typical example of the spectra is, as spectrum number 1 in Fig. 1e, the V-shaped pseudogap ( $\sim 0.2$  eV) spectrum with a small dip ( $\sim 20$  meV) near the Fermi energy. This is indistinguishable from those found in strongly underdoped cuprate superconductors<sup>3</sup>, and establishes that the pseudogap state appears locally at the nanoscale within the weak insulator. Besides the V-shaped pseudogap spectra in some areas, we find a new class of spectra that is predominant elsewhere in the insulating samples. As for example spectrum number 2 in Fig. 1e, such spectra are extremely asymmetric about the Fermi energy, U-shaped (concave in minus a few hundred millivolts) and exhibit no clear pseudogap. The growing asymmetry is strongly indicative of approaching the Mott insulating state<sup>15,16</sup> whereas the non-zero conductance in the unoccupied state is distinct from the Mott insulating state<sup>17</sup>. The approach for spectroscopic examination of the emergence of the pseudogap from the weak insulator is therefore transformation from the U-shaped insulating spectra to the V-shaped pseudogap spectra as a function of location and doping.

Figure 2a represents the transformation between these two types of spectrum. The V-shaped pseudogap becomes larger and broader, and eventually is smoothly connected to the U-shaped insulating spectra. To quantify this variation, we focus on positive biases where the edge of the pseudogap is clear. We fit the following function to each spectrum<sup>18</sup>,

$$f(E) = c_0 \operatorname{Re} \left[ \frac{E + i\Gamma(E)}{\sqrt{(E + i\Gamma(E))^2 - \Delta^2}} \right] + c_1 E + c_2 \quad (1)$$

where  $E$  is the energy,  $\Gamma$  is the broadening term,  $\Delta$  is the energy gap and  $c_i$  ( $i = 0, 1, 2$ ) are fitting constants. Use of equation (1) is merely for accurate quantitative parameterization of the gap maximum and does not imply any particular electronic state. We use  $\Gamma(E) = \alpha E$  as ref. 18 ( $\alpha$  is a proportional constant) but momentum-independent  $\Delta$  for simplicity of fitting procedures (see

<sup>1</sup>Inorganic Complex Electron Systems Research Team, RIKEN Advanced Science Institute, Wako, Saitama 351-0198, Japan, <sup>2</sup>Magnetic Materials Laboratory, RIKEN Advanced Science Institute, Wako, Saitama 351-0198, Japan, <sup>3</sup>Materials and Structures Lab., Tokyo Institute of Technology, Yokohama, Kanagawa 226-8503, Japan, <sup>4</sup>Institute for Integrated Cell-Material Sciences, Kyoto University, Sakyo-ku, Kyoto 606-8501, Japan, <sup>5</sup>LASSP, Department of Physics, Cornell University, Ithaca, New York 14853, USA, <sup>6</sup>CMPMS Department, Brookhaven National Laboratory, Upton, New York 11973, USA, <sup>7</sup>School of Physics and Astronomy, University of St Andrews, St Andrews KY16 9SS, UK, <sup>8</sup>Kavli Institute at Cornell for Nanoscale Science, Cornell University, Ithaca, New York 14853, USA, <sup>9</sup>Department of Physics, University of Tokyo, Hongo, Tokyo 113-0033, Japan. \*e-mail: kohsaka@riken.jp.

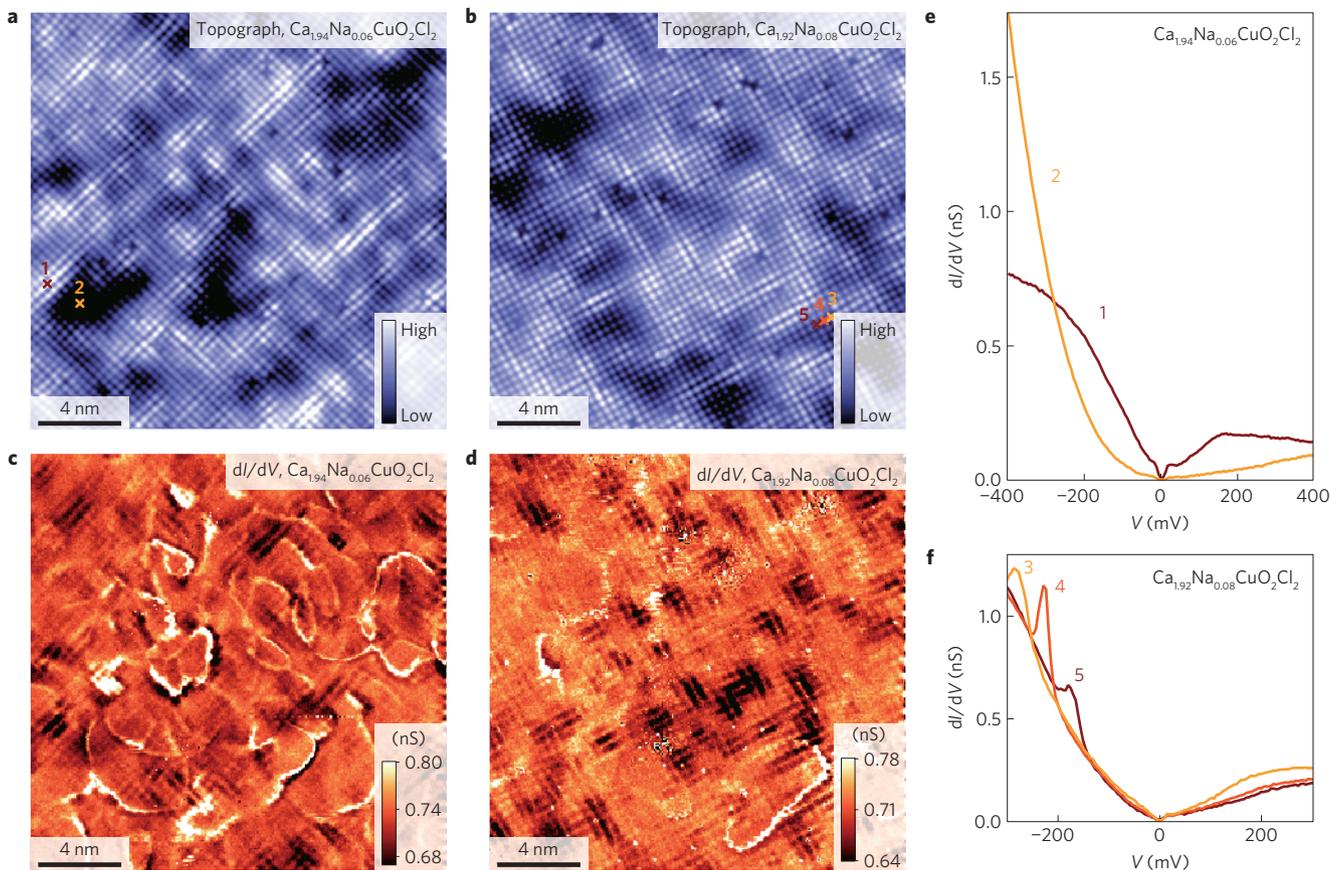


**Figure 1 | Spectral features unique to the insulating samples.** **a,b**,  $20 \times 20 \text{ nm}^2$  square constant-current topographic images of  $x = 0.06$  and  $x = 0.08$ , respectively. Scanning parameters are  $0.1 \text{ nA}$  at  $-0.4 \text{ V}$  for **a** and  $0.1 \text{ nA}$  at  $-0.3 \text{ V}$  for **b**. The markers with numbers indicate locations where spectra shown in **e** and **f** were taken. **c,d**, Differential conductance maps taken at  $-0.28 \text{ V}$  and  $-0.22 \text{ V}$  in the same field of view as in **a** and **b**, respectively. Scanning parameters are  $0.2 \text{ nA}$  at  $-0.4 \text{ V}$  for **c**, and  $0.15 \text{ nA}$  at  $-0.3 \text{ V}$  for **d**. The wavy, bright, arcs caused by the tip-induced impurity charging guarantee that these surfaces are insulating. **e,f**, Examples of differential conductance spectra taken in the insulating samples. Numbers denote locations where these spectra were taken in **a** and **b**. Peaks found in the spectra of **f** are caused by the tip-induced impurity charging. The set-up conditions of spectra in **e** and **f** are  $0.2 \text{ nA}$  at  $-0.4 \text{ V}$  and  $0.15 \text{ nA}$  at  $-0.3 \text{ V}$ , respectively.

also Supplementary Information). The results of fits are shown by the black curves superimposed on the experimental data in Fig. 2a. The excellent agreement between the data and the fits ensures the precision of extracted parameters. Moreover, the extracted  $\Delta$  and  $\alpha$  demonstrate that this fitting works to parameterize the variation of spectra through magnitude ( $\Delta$ ) and broadening in energy of the states at pseudogap energy.

On the basis of the successful fits, we plot spatial variation and doping evolution of  $\Delta$  and  $\alpha$  in Fig. 2b–e. The impurity charging clearly appears as wavy red and orange arcs in  $\alpha$ -maps, preventing us from extracting  $\alpha$  associated with the pseudogap where the wavy arcs appear. Nevertheless, the  $\Delta$ - and  $\alpha$ -maps exhibit large cross-correlations (correlation coefficients are 0.55 for  $x = 0.06$  and 0.59 for  $x = 0.08$ ), corroborating that the pseudogap spectrum gets broader with its increasing magnitude as holes are removed. Purple and blue areas are predominant in the  $x = 0.06$  sample (Fig. 2b). Spectra found in these areas are the U-shaped ones of the weak insulator as shown in Fig. 2a in the same colour. Orange and yellow areas in the  $\Delta$ -maps show a clear pseudogap as shown in Fig. 2a. Thus we find that, for bulk-insulating samples, the nanoscale pseudogap regions are embedded within the matrices of the weak insulator (Fig. 2b). As more holes are introduced, the pseudogap areas eventually become predominant and mutually connected near the insulator–superconductor critical doping (Fig. 2c). They eventually overwhelm the insulating areas of the underdoped superconducting sample (Fig. 3b).

The high spatial resolution of this new pseudogap analysis reveals that the spatial variation of  $\Delta$  itself is locally ordered rather than randomly dispersed. The atomically resolved  $\Delta$ -maps (Fig. 3a–d) clearly show that the spatial arrangement of the pseudogap energy  $\Delta(\mathbf{r})$  is typically elongated in a Cu–O bond direction and forms bond-like objects on Cu–O–Cu complexes. Such bond-like objects then align to each other in the direction normal to the bonds and organize themselves into nanometre-scale unidirectional clusters. Given the excellent agreement of the fit, these ordered structures in the  $\Delta$ -maps indicate that the spectral shape is spatially modulated over quite a wide energy range. Therefore, spatial variation of the local density-of-states (LDOS) extracted appropriately is expected to have similar spatial structures.

To confirm this, we calculate the  $R$ -maps,  $R(\mathbf{r}, E) \equiv I(\mathbf{r}, +E)/I(\mathbf{r}, -E) = \int_0^E N(\mathbf{r}, \varepsilon) d\varepsilon / \int_{-E}^0 N(\mathbf{r}, \varepsilon) d\varepsilon$ , where  $I$  and  $N$  are the tunnelling current and the LDOS, respectively, at the location  $\mathbf{r}$  and the energy  $E$  (ref. 3). By choosing an appropriate energy window of the integration, we can map the LDOS variation around the pseudogap energy onto a single image of the  $R$ -map without any influence of the intense electronic heterogeneity<sup>19</sup>. As shown in Fig. 3e,f, the  $R$ -maps obviously show the same structures as those of the  $\Delta$ -maps in both the atomic and nanometre scale. We therefore conclude that the pseudogap state breaks translational and rotational symmetry of the lattice in the form of the unidirectional clusters consisting of the bond-like objects on Cu–O–Cu complexes.

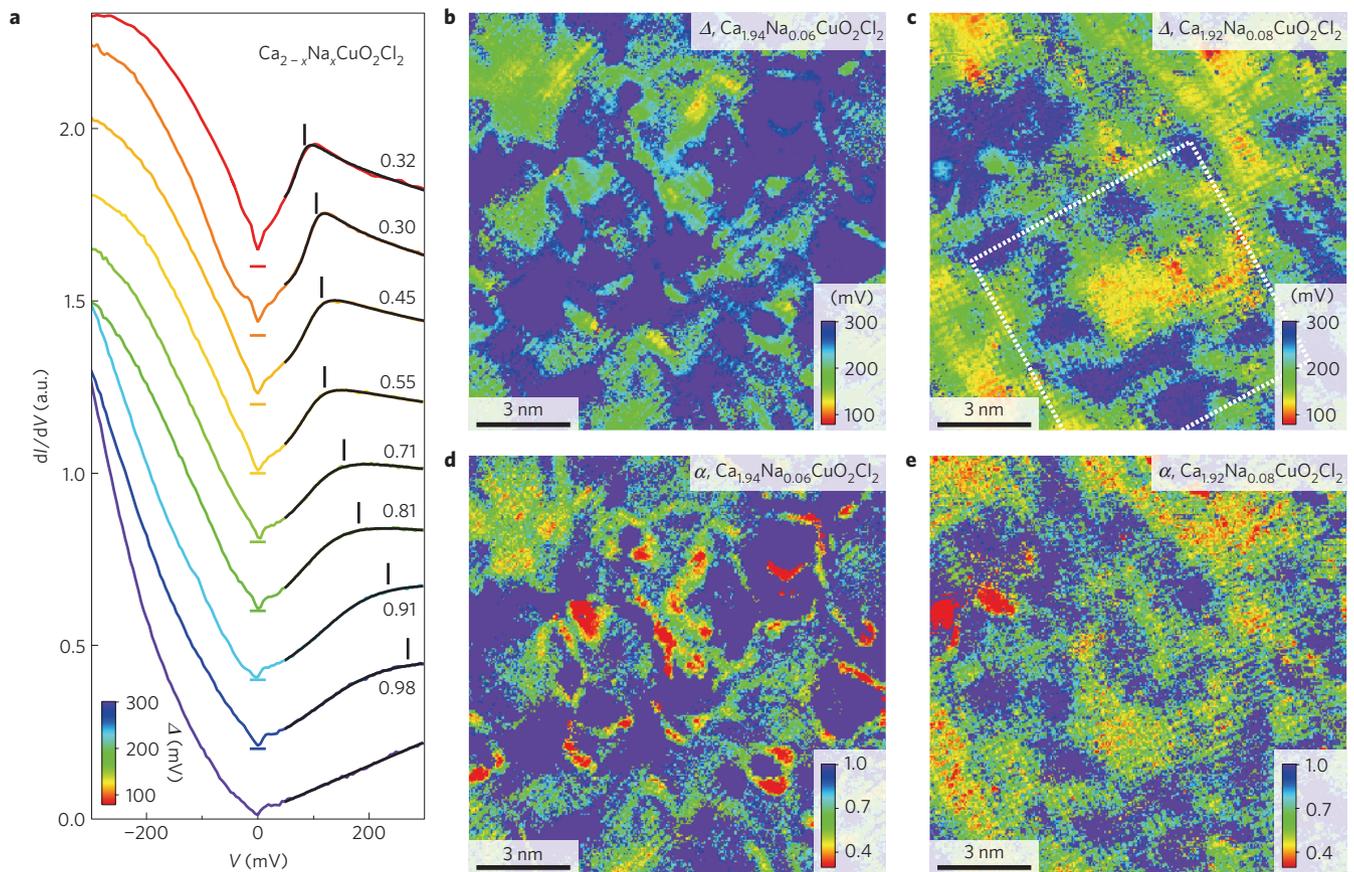


**Figure 2 | Spatial variations and doping evolution of the pseudogap.** Examples of differential conductance spectra taken at various locations of multiple samples of  $0.06 \leq x \leq 0.12$ . Each spectrum is shifted vertically for clarity and colour-coded on the basis of the values of  $\Delta$  with the colour scale the same as used in **b** and **c**. The horizontal markers indicate zero of each curve. The black curves superimposed on the spectra are the results of fits described in the text. The vertical markers denote extracted  $\Delta$  and the numbers denote  $\alpha$ . **b–e**,  $20 \times 20 \text{ nm}^2$  square  $\Delta$ -maps and  $\alpha$ -maps of  $x = 0.06$  and  $x = 0.08$ . The original  $256 \times 256$  spectra were taken in the same fields of view as in Fig. 1a and b, respectively. Note that colour scales are common to **b** and **c**, and **d** and **e**. The white dotted square in **c** shows the area of Fig. 3a.

To analyse the broken symmetry observed in the  $\Delta$ - and the  $R$ -maps, we focus on local symmetry of the maps. To separate  $C_{2v}$  symmetry of the bond-like objects from  $C_{4v}$  symmetry of the lattice, we measure the following two components about each unit cell,  $Q_{xx}(f; \mathbf{r}_{\text{Cu}}) = \sum_{i=1}^4 (-1)^i f(\mathbf{r}_{\text{O}(i)})$  and  $Q_{xy}(f; \mathbf{r}_{\text{Cu}}) = \sum_{i=1}^4 (-1)^i f(\mathbf{r}_{\text{O}'(i)})$ , where  $f$  is a two-dimensional image and  $\mathbf{r}_{\text{O}(i)}$  is the locations of four oxygen atoms surrounding a copper atom at the location  $\mathbf{r}_{\text{Cu}}$  as illustrated in the inset of Fig. 4h.  $\mathbf{r}_{\text{O}'(i)}$  is the location given by  $45^\circ$  rotation of  $\mathbf{r}_{\text{O}(i)}$  about the central copper. Either  $Q_{xx}$  or  $Q_{xy}$  (or both) is non-zero for  $C_{2v}$  patterns and both of them are zero for  $C_{4v}$  patterns (see also Supplementary Information).

The  $Q_{xx}$  and  $Q_{xy}$  about the  $\Delta$ - and  $R$ -maps shown in Fig. 4 quantitatively visualize how those maps break the lattice symmetry and form short-range order. The bond-like objects and the nanometre-scale unidirectional clusters are expressed as bars and arrays of bars, as exemplified by the rectangles in Figs 3 and 4. These bars and arrays are closely arranged in  $Q_{xx}$  rather than  $Q_{xy}$ , evidently showing that the  $C_{2v}$  symmetry breaking occurs in the direction not diagonal but parallel to the Cu–O bond. Meanwhile, as shown by the ovals in Fig. 4a–d, areas without clear bars in both  $Q_{xx}$  and  $Q_{xy}$  are found in  $x = 0.08$ , indicating the symmetry of patterns is  $C_{4v}$ . Given that U-shaped insulating spectra are found in large- $\Delta$  areas whereas V-shaped pseudogap spectra are found in small- $\Delta$  areas, we find that larger electron–hole asymmetry (smaller  $R$ ) and U-shaped insulating spectra are found in the  $C_{4v}$  areas whereas smaller electron–hole asymmetry (larger  $R$ ) and

clear V-shaped pseudogap spectra are found in the  $C_{2v}$  areas by comparing Figs 3 and 4. This further supports that the pseudogap state breaks the symmetry of the lattice. Large correlation between  $Q_{xx}(\Delta)$  and  $Q_{xx}(R)$ ,  $-0.45$  for Fig. 4a,c and  $-0.60$  for Fig. 4e,g, quantitatively confirms similarity between the  $\Delta$ - and  $R$ -maps about the local broken symmetry.

Our results reveal new perspectives on the genesis of the cuprate pseudogap state<sup>20</sup>. First, the pseudogap regions emerge at the lowest doping levels as nanometre-scale clusters that are embedded in the  $C_4$ -symmetric matrices of a weak insulator. This implies that short-range localization of the doped holes and strong interaction between them is the first step in the formation of the pseudogap state out of the Mott insulator. Second, we discovered that the pseudogap energy scale itself  $\Delta(\mathbf{r})$  exhibits strong breaking of  $C_4$ -symmetry down to the  $C_{2v}$  symmetry, at the unit-cell scale within these clusters. Third, the spatial boundaries between  $C_{2v}$  (pseudogap) and  $C_{4v}$  (insulating) areas can be atomically sharp as highlighted by the neighbouring ovals and rectangle in Fig. 3a,e. This indicates that although the pseudogap state is a distinctive electronic phase, it can exist as short-range order<sup>11</sup>. Fourth, the width of  $C_{2v}$  clusters is constantly about  $4a_0$  ( $a_0$ : distance between nearest copper atoms) independently of doping of  $0.06 \leq x \leq 0.12$  (see also Supplementary Information). Moreover, the  $C_{2v}$  clusters are aligned with the Cu–O bonds in the whole doping range studied, indicating that this form of unit-cell-scale rotational symmetry breaking<sup>3,4</sup> is an elementary characteristic of the pseudogap phase.

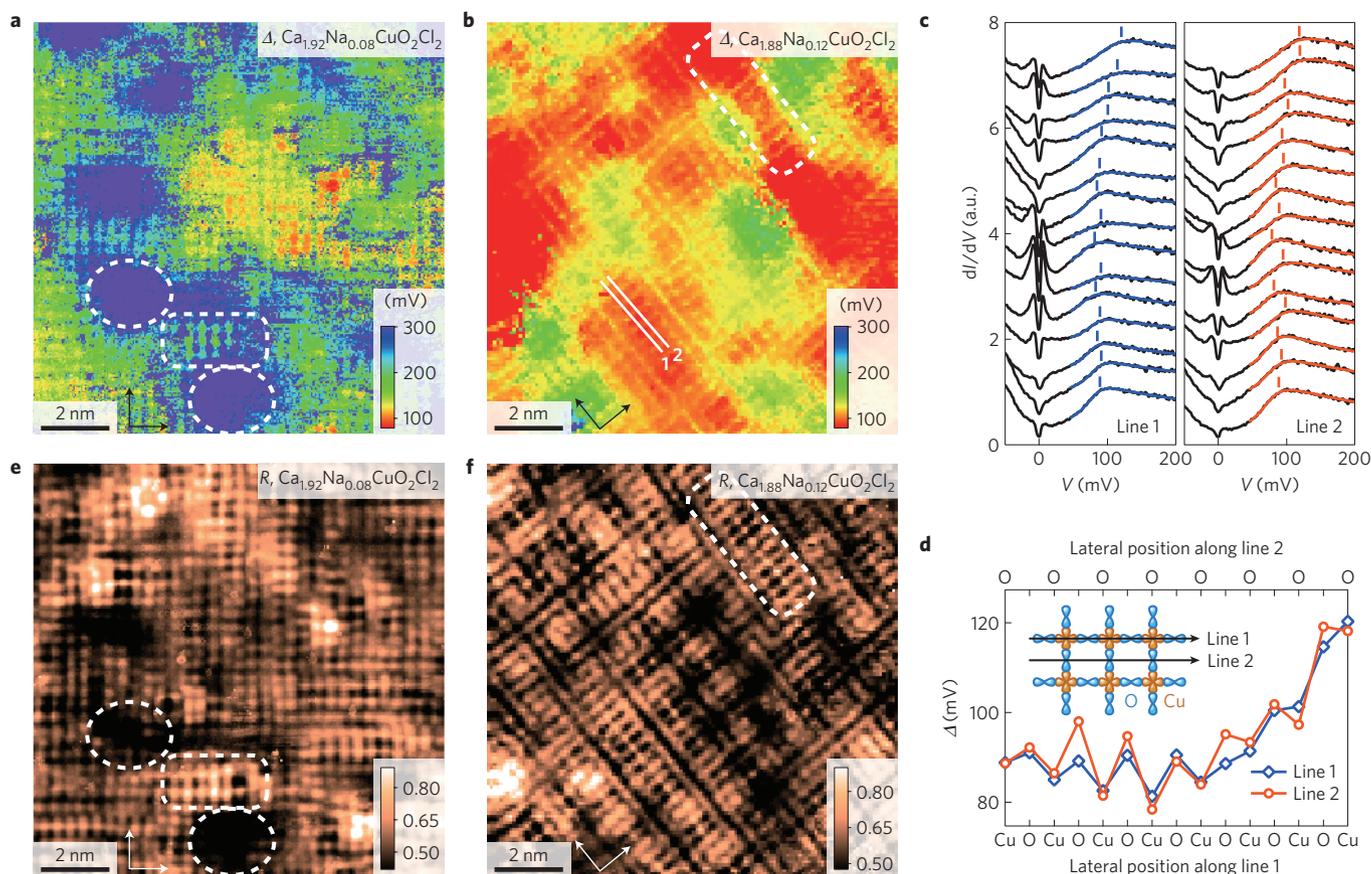

**Figure 3 | Atomic and nanoscale short-range order of the pseudogap state found in  $\Delta$ -maps and  $R$ -maps. **a, b**,  $12 \times 12 \text{ nm}^2$  square  $\Delta$ -maps of  $x = 0.08$  and  $x = 0.12$ , respectively. **a** was taken in the area shown by the white dotted square in Fig. 2c. **b** was taken in the same area of the same sample used in ref. 3. The colour scale is the same as used in Fig. 2b,c. The black arrows indicate directions of Cu-O bonds. The solid lines in **b** are trajectories along which spectra shown in **c** were taken. **c**, Differential conductance spectra of  $\text{Ca}_{1.88}\text{Na}_{0.12}\text{CuO}_2\text{Cl}_2$  taken along lines 1 and 2 shown in **b**, demonstrating  $\Delta$  is actually modulated at the atomic scale. Each observed black spectrum is shifted vertically for clarity. Results of the fit, blue and orange in colour, are superimposed on the observed spectra. The markers denote extracted  $\Delta$ . **d**,  $\Delta$  extracted from fits to the spectra shown in **c**. The inset depicts the location of the trajectories where the spectra shown in **c** were taken, relative to the  $\text{CuO}_2$  plane.  $\Delta$  is modulated along the trajectories in the same manner at the atomic scale, leading to the formation of bond-like objects on Cu-O-Cu complexes. **e, f**,  $12 \times 12 \text{ nm}^2$  square  $R$ -maps taken in the same areas as **a** and **b**, respectively. The integration voltages are 252 meV for **e** and 150 meV for **f**. The white arrows indicate directions of Cu-O bonds. The dashed ovals and rectangles are guides to the eye indicating an area with no clear pseudogap, a clear pseudogap and the nanometre-scale unidirectional clusters consisting of the bond-like objects, respectively.**

All of the above observations reveal that hole doping into the  $C_4$ -symmetric weak insulator is not a homogeneous process in  $\text{Ca}_{2-x}\text{Na}_x\text{CuO}_2\text{Cl}_2$ . Rather it proceeds by localization of doped holes into  $C_{2v}$ -symmetric nanoclusters embedded in the  $C_4$ -symmetric insulator so that the bulk materials must exhibit a fundamentally heterogeneous two-component electronic structure<sup>11</sup>. This situation persists until, with increasing dopant density, the  $C_{2v}$  pseudogap clusters become interconnected (percolate) at  $x = 0.08$ , coincident with the appearance of long-range superconductivity. This observation seems to imply a beneficial rather than competing role for the pseudogap phase in the appearance of cuprate high-temperature superconductivity.


## Methods

The  $\text{Ca}_{2-x}\text{Na}_x\text{CuO}_2\text{Cl}_2$  crystals used in this study were grown by the flux method under high pressure of several gigapascals<sup>21</sup>. The samples of  $x = 0.06, 0.08$  and  $0.12$  are insulators, insulators (in the close vicinity of the insulator-superconductor critical doping) and underdoped superconductors of  $T_c = 21 \text{ K}$ , respectively<sup>21,22</sup>. The samples were cleaved at 77 K or below and immediately transferred to the heads of microscopes cooled down beforehand. All measurements were done at 4.6 K or below with tungsten tips. The tips were prepared by field emission on gold or field evaporation with field ion microscopes. Differential conductance was measured by the standard lock-in technique with modulation voltages of 1–5 mV. The bias voltages are applied to the sample.

Received 29 November 2011; accepted 17 April 2012;  
published online 20 May 2012

## References

- Zaenen, J., Sawatzky, G. A. & Allen, J. W. Band gaps and electronic structure of transition-metal compounds. *Phys. Rev. Lett.* **55**, 418–421 (1985).
- Chen, C. T. *et al.* Electronic states in  $\text{La}_{2-x}\text{Sr}_x\text{CuO}_{4+\delta}$  probed by soft-X-ray absorption. *Phys. Rev. Lett.* **66**, 104–107 (1991).
- Kohsaka, Y. *et al.* An intrinsic bond-centered electronic glass with unidirectional domains in underdoped cuprates. *Science* **315**, 1380–1385 (2007).
- Lawler, M. J. *et al.* Intra-unit-cell electronic nematicity of the high- $T_c$  copper-oxide pseudogap states. *Nature* **466**, 347–351 (2010).
- Sakurai, Y. *et al.* Imaging doped holes in a cuprate superconductor with high-resolution Compton scattering. *Science* **332**, 698–702 (2011).
- Takagi, H. *et al.* Systematic evolution of temperature-dependent resistivity in  $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ . *Phys. Rev. Lett.* **69**, 2975–2978 (1992).
- Ando, Y., Lavrov, A. N., Komiya, S., Segawa, K. & Sun, X. F. Mobility of the doped holes and the antiferromagnetic correlations in underdoped high- $T_c$  cuprates. *Phys. Rev. Lett.* **87**, 017001 (2001).
- Lee, J. *et al.* Spectroscopic fingerprint of phase-incoherent superconductivity in the underdoped  $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ . *Science* **325**, 1099–1103 (2009).
- Mesaros, A. *et al.* Topological defects coupling smectic modulations to intra-unit-cell nematicity in cuprates. *Science* **333**, 426–430 (2011).
- Fradkin, E., Kivelson, S. A., Lawler, M. J., Eisenstein, P. J. & Mackenzie, A. P. Nematic Fermi fluids in condensed matter physics. *Annu. Rev. Condens. Matter Phys.* **1**, 153–178 (2010).

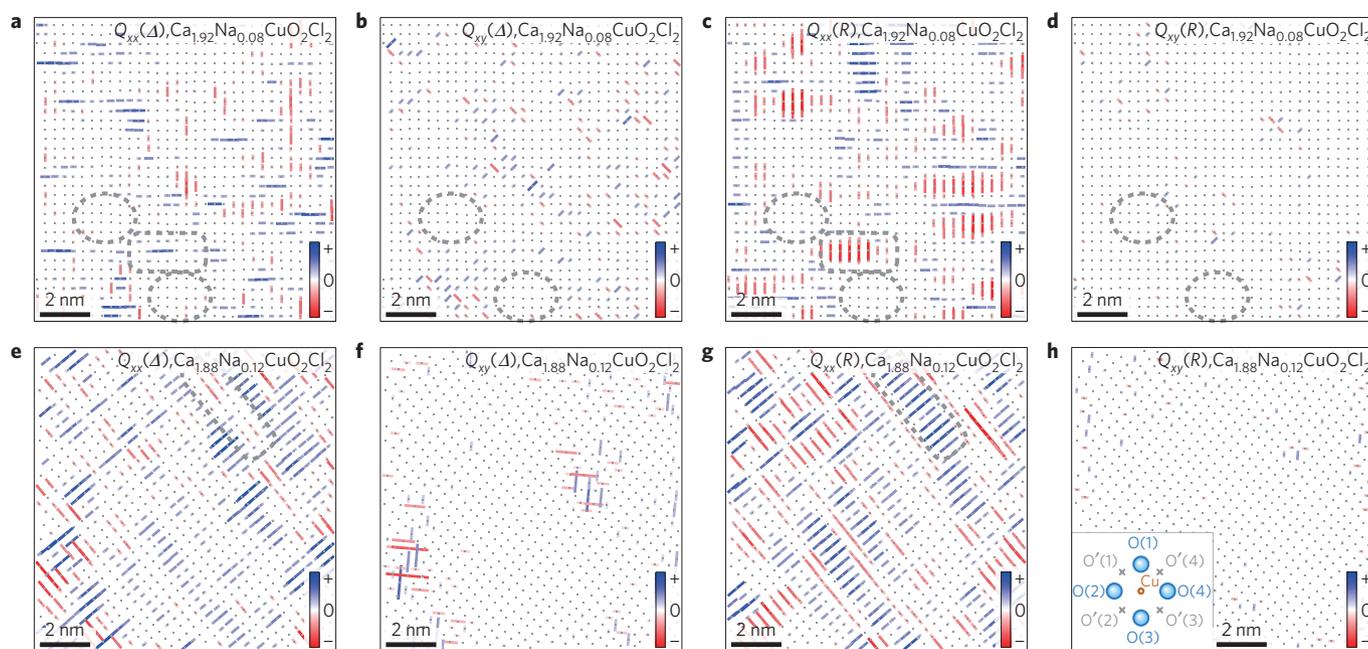

**Figure 4 | Quantitative analysis of local symmetry corroborating that the pseudogap state accompanies local  $C_2$  symmetry.** The values of  $Q_{xx}$  and  $Q_{xy}$  at each copper site indicated by the grey dots are expressed by the short bars. The length of the bars denotes the magnitude of  $Q_{xx}$  and  $Q_{xy}$ . The colour of the bars carries the same information as the length does for clarity. The direction of each bar corresponds to the sign of  $Q_{xx}$  and  $Q_{xy}$ . The left (**a, b, e, f**) and the right (**c, d, g, h**) four panels are computed for the  $\Delta$ - and  $R$ -maps, respectively. The upper (**a-d**) and lower (**e-h**) panels are computed for  $x = 0.08$  and  $x = 0.12$ , respectively. The ovals in **a-d** and the rectangles in **a, c, e** and **g** are drawn at the same location as those in Fig. 3. The first and third columns (**a, c, e, g**) and second and fourth columns (**b, f, d, h**) are  $Q_{xx}$  and  $Q_{xy}$ , respectively. The original  $\Delta$ - and  $R$ -maps are shown in Fig. 3. The inset of **h** depicts the locations of  $r_{Cu}$ ,  $r_{O(i)}$  and  $r_{O'(i)}$  used in the definition of  $Q_{xx}$  and  $Q_{xy}$  described in the text.

- Dagotto, E. Complexity in strongly correlated electronic systems. *Science* **309**, 257–262 (2005).
- Pradhan, N. A., Liu, N., Silien, C. & Ho, W. Atomic scale conductance induced by single impurity charging. *Phys. Rev. Lett.* **94**, 076801 (2005).
- Marczinowski, F., Wiebe, J., Meier, F., Hashimoto, K. & Wiesendanger, R. Effect of charge manipulation on scanning tunneling spectra of single Mn acceptors in InAs. *Phys. Rev. B* **77**, 115318 (2008).
- Teichmann, K. *et al.* Controlled charge switching on a single donor with a scanning tunneling microscope. *Phys. Rev. Lett.* **101**, 076103 (2008).
- Randeria, M., Sensarma, R., Trivedi, N. & Zhang, F.-C. Particle-hole asymmetry in doped Mott insulators: Implications for tunneling and photoemission spectroscopies. *Phys. Rev. Lett.* **95**, 137001 (2005).
- Anderson, P. W. & Ong, N. P. Theory of asymmetric tunneling in the cuprate superconductors. *J. Phys. Chem. Solids* **67**, 1–5 (2006).
- Ye, *c et al.* Visualizing the atomic scale electronic structure of the  $Ca_2CuO_2Cl_2$  Mott insulator. Preprint at <http://arxiv.org/abs/1201.0342> (2012).
- Allredge, J. W. *et al.* Evolution of the electronic excitation spectrum with strongly diminishing hole density in superconducting  $Bi_2Sr_2CaCu_2O_{8+\delta}$ . *Nature Phys.* **4**, 319–326 (2008).
- Kohsaka, Y. *et al.* How Cooper pairs vanish approaching the Mott insulator in  $Bi_2Sr_2CaCu_2O_{8+\delta}$ . *Nature* **454**, 1072–1078 (2008).
- Hüfner, S., Hossain, M. A., Damascelli, A. & Sawatzky, G. A. Two gaps make a high-temperature superconductor? *Rep. Prog. Phys.* **71**, 062501 (2008).
- Kohsaka, Y. *et al.* Growth of Na-doped  $Ca_2CuO_2Cl_2$  single crystals under high pressures of several GPa. *J. Am. Chem. Soc.* **124**, 12275–12278 (2002).
- Waku, K. *et al.* Charge dynamics of  $Ca_{2-x}Na_xCuO_2Cl_2$  as a correlated electron system with the ideal tetragonal lattice. *Phys. Rev. B* **70**, 134501 (2004).

### Acknowledgements

We gratefully acknowledge discussions with M. Lawler and E-Ah Kim. Studies at Brookhaven/ Cornell are supported by the Center for Emergent Superconductivity, an Energy Frontier Research Center, under DE-2009-BNL-PM015, and studies at RIKEN by JSPS KAKENHI (19840052, 20244060).

### Author contributions

Y.K., M.A. and M.T. grew single crystals. Y.K. and T.H. performed STM measurements. Y.K. analysed data. Y.K. and J.C.D. wrote the manuscript. J.C.D. and H.T. supervised the project.

### Additional information

The authors declare no competing financial interests. Supplementary information accompanies this paper on [www.nature.com/naturephysics](http://www.nature.com/naturephysics). Reprints and permissions information is available online at [www.nature.com/reprints](http://www.nature.com/reprints). Correspondence and requests for materials should be addressed to Y.K.